

Revista IBRACON de Estruturas e Materiais



Todo o conteúdo deste periódico, exceto onde está identificado, está licenciado sob uma [Licença Creative Commons](#).

Fonte: http://www.scielo.br/scielo.php?script=sci_arttext&pid=S1983-41952013000500002&lng=en&nrm=iso. Acesso em: 27 nov. 2020.

REFERÊNCIA

OLIVEIRA, M. H. *et al.* Punching resistance of internal slab-column connections with double-headed shear studs. **Revista IBRACON de Estruturas e Materiais**, São Paulo, v. 6, n. 5, p. 681-714, out. 2013. DOI: <http://dx.doi.org/10.1590/S1983-41952013000500002>. Disponível em: http://www.scielo.br/scielo.php?script=sci_arttext&pid=S1983-41952013000500002&lng=en&nrm=iso. Acesso em: 27 nov. 2020.

Punching resistance of internal slab-column connections with double-headed shear studs

Resistência à punção de ligações laje-pilar interno com conectores de cisalhamento



M. H. OLIVEIRA ^a
honorato.eng@gmail.com.br

M. J. M. PEREIRA FILHO ^b

D. R. C. OLIVEIRA ^c
mpina@ufpa.br

M. P. FERREIRA ^d
denio@ufpa.br

G. S. S. A. MELO ^e
melog@unb.br

Abstract

Punching shear is a brittle failure mode that may occur in slab-column connections, which may be prevented by using shear reinforcement in the slab-column connection. This paper presents comparisons between experimental results of 36 tests in internal slab-column connections with double-headed shear studs, which are largely used in North America, Europe and Asia, with theoretical results using recommendations presented by ACI 318, NBR6118, Eurocode 2 and also the Critical Shear Crack Theory (CSCT). Considering the database used it is possible to observe that ACI 318 presents conservative trends, whereas NBR 6118 showed a low coefficient of variation, but with a large number of unsafe results. Both Eurocode 2 and CSCT showed satisfactory results with Eurocode 2 presenting slightly higher performance.

Keywords: flat slabs, punching shear, double-headed studs.

Resumo

A punção é uma forma de ruptura por cisalhamento que pode ocorrer em ligações laje-pilar que pode ser evitada utilizando-se armaduras de cisalhamento na ligação. Este artigo apresenta comparações entre resultados experimentais de 36 ensaios realizados em ligações laje-pilar interno, armadas com conectores de cisalhamento do tipo pino de duas cabeças, populares na América do Norte, Europa e Ásia, com resultados teóricos utilizando as recomendações do ACI 318, NBR 6118, Eurocode 2, além da Teoria da Fissura Crítica de Cisalhamento (TFCC). Para o banco de dados utilizado, o ACI 318 mostrou tendências conservadoras, enquanto que a NBR 6118 mostrou baixo coeficiente de variação, mas um grande número de resultados contra a segurança. Tanto o Eurocode 2, quanto a TFCC apresentaram resultados satisfatórios, com o Eurocode 2 apresentando desempenho ligeiramente superior.

Palavras-chave: lajes lisas, punção, conectores de cisalhamento.

^a Professor, Departamento de Engenharia Civil, Universidade Federal de Goiás, honorato.eng@gmail.com.br, Catalão, Goiás, Brasil.

^b Engenheiro Civil, Mestrando em Estruturas, Faculdade de Engenharia Civil, Universidade Federal do Pará, Belém, Pará, Brasil.

^c Professor, Faculdade de Engenharia Civil, Universidade Federal do Pará, mpina@ufpa.br, Belém, Pará, Brasil.

^d Professor, Faculdade de Engenharia Civil, Universidade Federal do Pará, denio@ufpa.br, Belém, Pará, Brasil.

^e Professor, Departamento de Engenharia Civil e Ambiental, Universidade de Brasília, melog@unb.br, Brasília, Distrito Federal, Brasil.

1. Introduction

Flat slabs are laminated reinforced or prestressed concrete structures that are supported directly on columns. Its use is common in North American, European and Asian countries. In Brazil, this constructive system begins to stand out in the market of civil construction, mainly for its greater simplicity in the execution of the forms and rebars. Such situation can lead to reductions in labor costs and in construction time, besides attributing greater flexibility in the use of the built spaces.

Punching is a brittle failure mode by shear that may occur in structural elements such as slabs when submitted to concentrated loads or reactions, which may lead the structure to ruin through the progressive collapse. The punching shear resistance slab-column connection is one of the most important parameters in the design of flat slabs. During design, it is possible to reduce the intensity of the shear stresses in the slab-column connection through the located increase of the thickness of the slab by using drop panels or column capitals. Nevertheless, the best technical alternative to increase the punching resistance of slab-column connections is the use of shear reinforcement. Among the several kinds of shear reinforcements available, stand out the double-headed studs, which are very popular nowadays in constructions with flat slabs, mainly due to its efficient mechanical anchorage provided by the heads, which are forged to the rebars.

This paper aims to evaluate the recommendations presented by some of the main design codes for the estimation of punching resistance of reinforced concrete flat slabs with double-headed studs as shear reinforcement. This is performed through the comparison of the experimental results of 36 tests on flat slabs with the theoretical results obtained according to the recommendations presented by ACI 318M [1], Eurocode 2 [2] and NBR 6118 [3]. The experimental results are also compared to those obtained using the Critical Shear Crack Theory (CSCT) as presented by Ruiz and Muttoni [4]. These comparisons are relevant especially because the last version of ACI and the recent version of *fib Model Code 2010* [5] (based on CSCT) present specific treatments for the cases of slabs with studs as shear reinforcement.

2. Shear reinforcement

In the design of a slab-column connections, if it is found that they do not meet safety limits regarding punching, its resistance may be enhanced adopting some actions, as the increase of the column section, of the slab thickness, of the flexural reinforcement ratio, of the compressive strength of concrete, or by using drop panels and column capitals. However, the increase of the column section or the use drop panels and capitals usually generate problems from the architectural point of view. The increase of the slab thickness may mean a substantial elevation of the structure and foundation costs. Finally, increasing either the flexural reinforcement ratio or the compressive strength of concrete would have poor efficiency. Thus, when it is desirable to increase the punching resistance, one of the most practicable solutions may be the use of shear reinforcement.

The efficiency of the shear reinforcement regarding the punching resistance of slab-column connections relies on several aspects, like the kind of reinforcement used, and the amount, arrangement, spacing and the number of perimeters used. It is also essential for their

performance that appropriate anchoring conditions are guaranteed, being this, normally a critical point for most of the options of available reinforcements, once that slabs are slender elements. Other important aspect about the use of shear reinforcements in flat slabs refers to the practicality of its installation. The slab-column connection is submitted to high normal and shear stresses, being common the concentration of flexural bars in this area, what makes it difficult the distribution of shear reinforcements.

Several kinds of shear reinforcements were tested seeking to evaluate its efficiency. The first reinforcement tested in flat slabs were bent-up bars as the ones presented in Figure 1a. This kind of reinforcement was used in tests as the ones by Graf [6], Elstner and Hognestad [7] and Andersson [8]. They can be very efficient in increasing the punching resistance, provided that precautions are taken to avoid punching failures in the area immediately after the bent-up bars. For this purpose, it might be useful to combine other kinds of shear reinforcement with bent-up bars. Broms [9] associated bent-up bars in the first two perimeters with closed stirrups and was able to avoid punching failures.

Stirrups may also be used as shear reinforcement in flat slabs, having been tested closed stirrups (Figure 1b), one-legged open stirrups (Figure 1c), continuous u-shaped reinforcement like "shear combs" (Figure 1d), inclined stirrups (Figure 1e), among others. Closed and u-shaped stirrups are of difficult use because of building issues related to its assembly. One-legged stirrups showed poor anchorage in tests with flat slabs, even when adopting actions like bending its ends in 90° or 180° angles, or using horizontal bars passing inside these folds, as observed by Regan and Samadian [10]. Only inclined stirrups, as the ones used by Oliveira *et al.* [11] with a 60° inclination, have shown to be efficient in increasing the punching resistance.

Studs (Figures 1f and 1g) have been largely used due to their good mechanical anchorage and once they are industrialized, it is easier to ensure a higher quality, and eliminate some activities of the construction site. Although studs are difficult to install, especially if the designer adopts a radial arrangement for them, they are the most popular shear reinforcement in the civil construction industry today. Figure 1h presents shear heads, which are made with steel standard sections embedded in the connection. It is a type of reinforcement considered of a high cost, normally used when there is the necessity to let large holes in the area close to the connection and demand big adjusts in the flexural reinforcement around this area.

For cases of symmetric punching the distribution of the shear stresses around the slab-column connection is uniform. Thus, theoretically, the ideal would be to adopt a radial arrangement for the reinforcement, as indicated in Figure 2a. However, distributing the shear reinforcements in a radial shape usually generates big interferences with flexural reinforcements in the slab-columns connection. One alternative is to concentrate the shear reinforcement in orthogonal zones in a cruciform arrangement, as presented in Figure 2b. With the exception of ACI, the other design codes use to penalize the punching resistance estimations for cases of connections with cruciform arrangements, considering in a general manner, that this would only be justified in cases of columns with high rectangularity index or for slab-column connections in panels with substantial asymmetry in terms of loading or geometry.

The shear reinforcement ratio and the number of perimeters of shear reinforcement surrounding the column or loaded area

Figure 1 – Types of shear reinforcement for slab-column connections

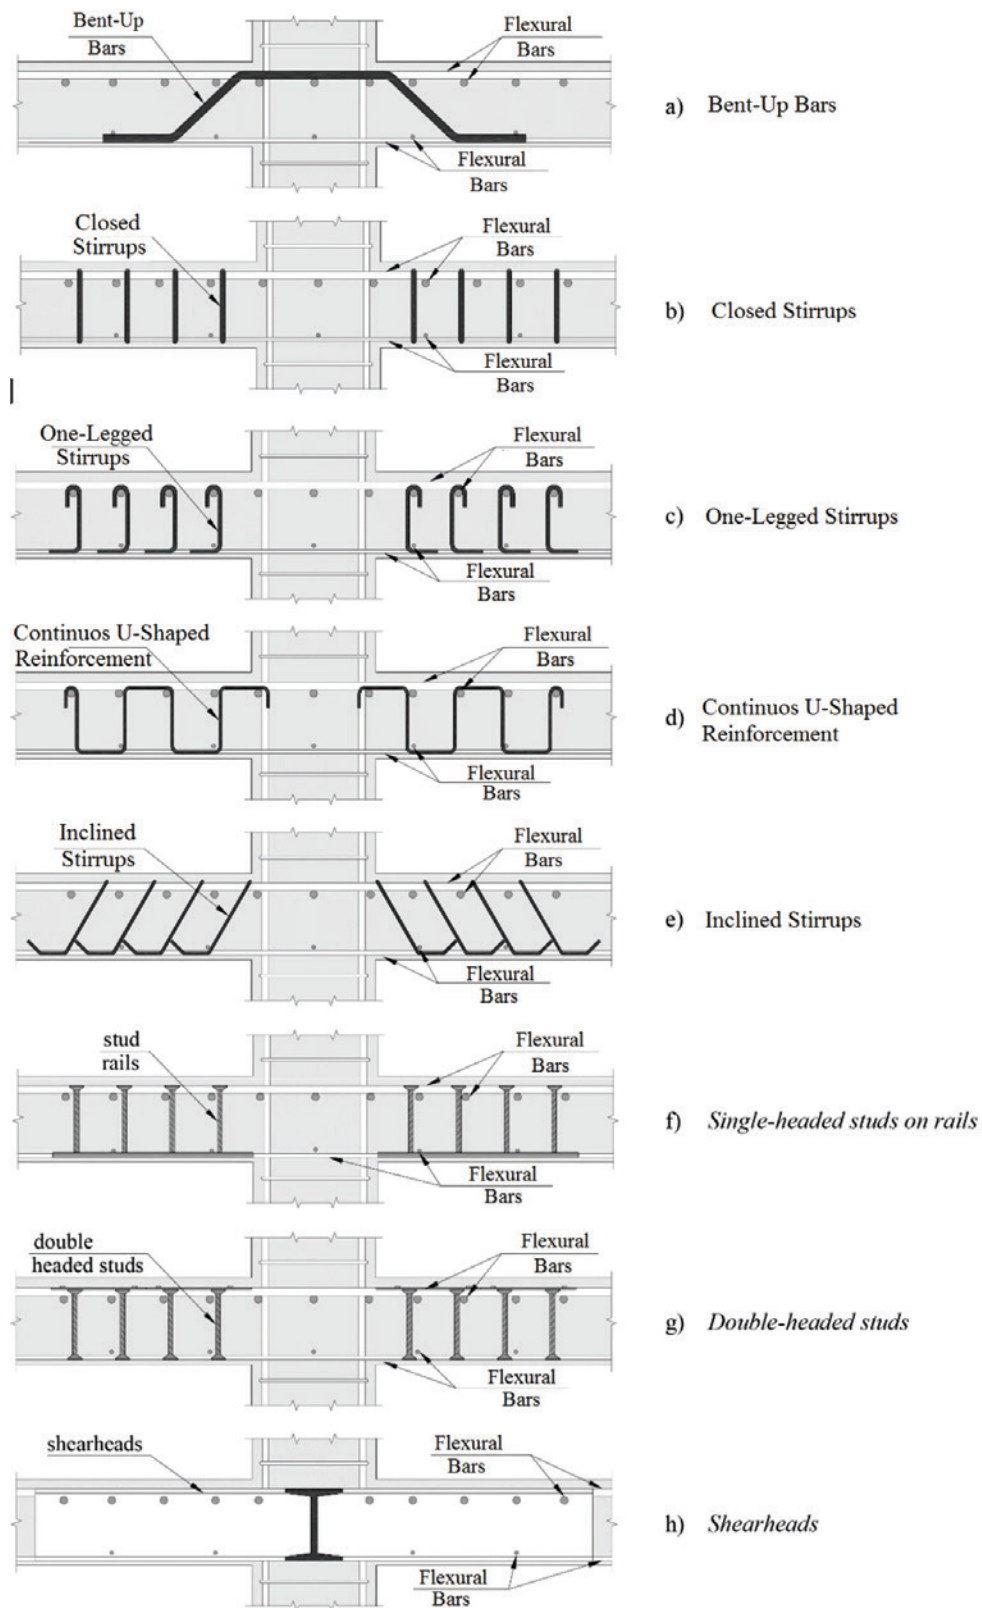


Figure 2 – Different arrangements for shear reinforcements

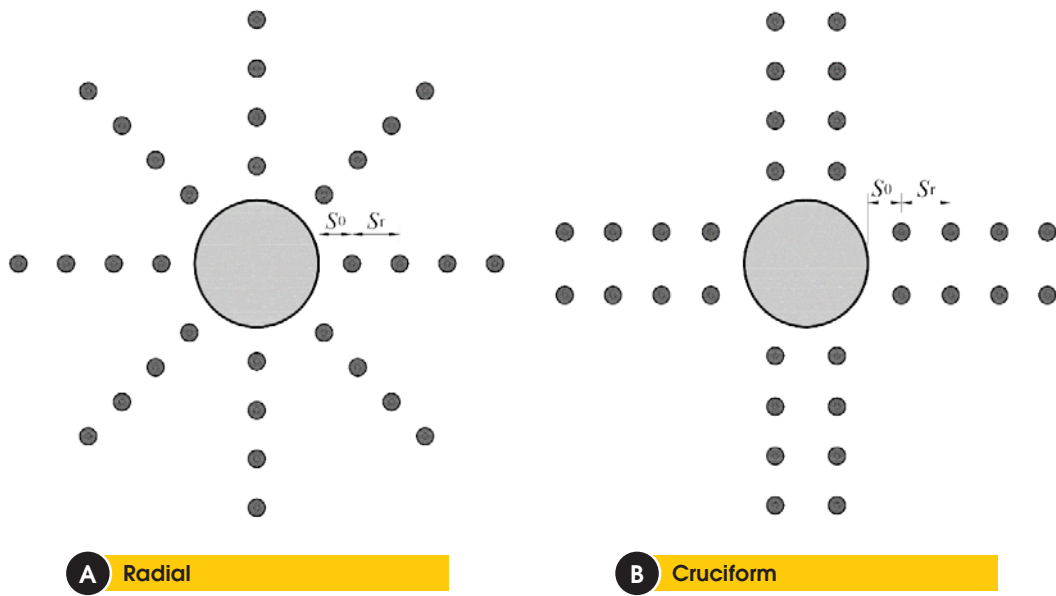


Figure 3 – Punching shear failure modes for slabs with shear reinforcement


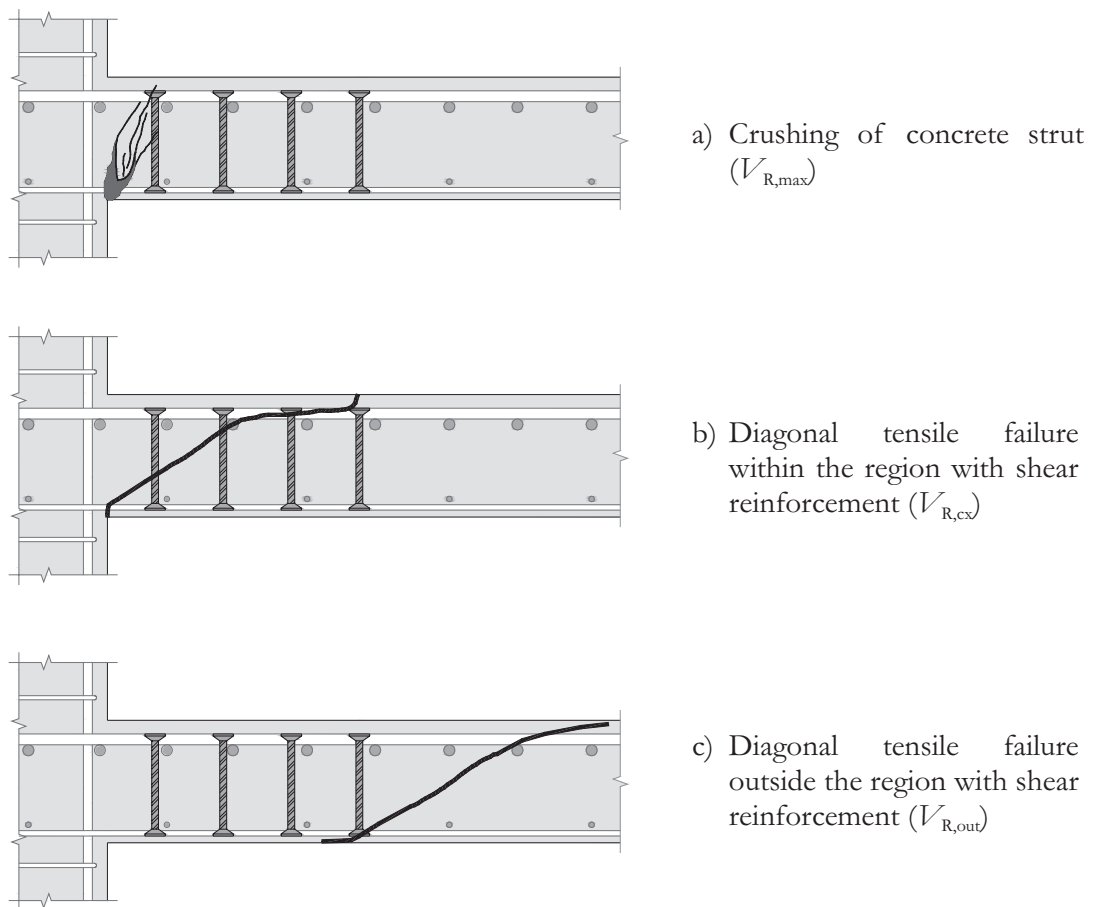


Figure 4 – Influence of the shear reinforcement in the load-displacement response - Dilger and Ghali (11)

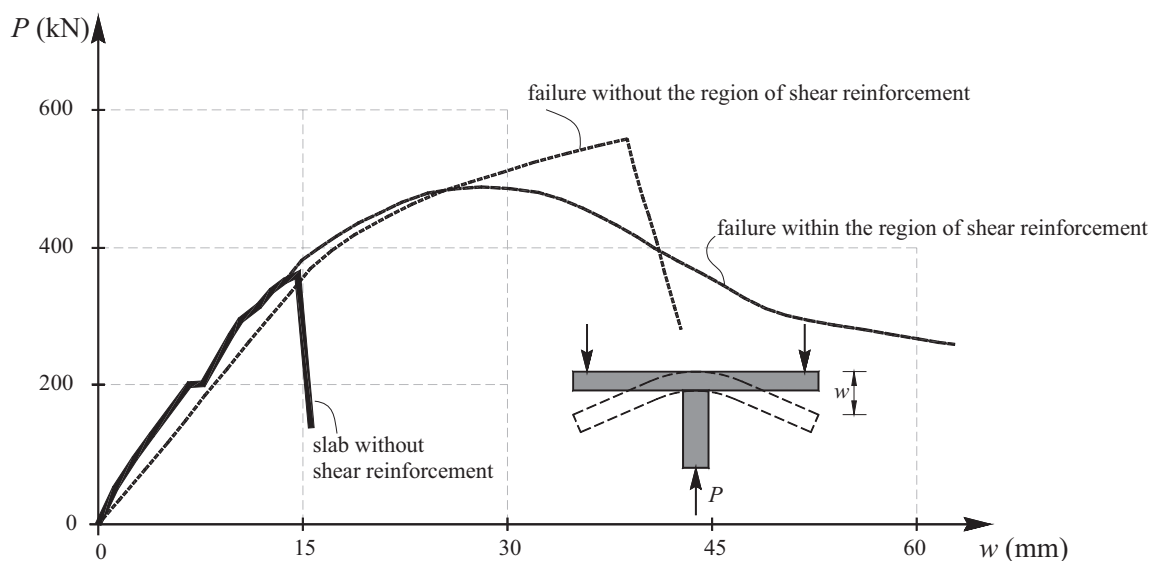

influence directly the punching shear failure mode, which may occur by crushing of a diagonal strut close to the column face or by diagonal tensile inside or outside the shear reinforced zone, as illustrated in Figure 3. Experimental evidences indicate that the position of punching failure cone substantially influences the ductility of the slab-column connection after the rupture. Figure 4, adapted from Dilger and Ghali [12], shows that when the rupture occurs out of the area reinforced to shear, the ruin can be as brusque as in the case of slabs without shear reinforcement.


Other important parameter in the definition of the punching resistance of slab-column connections is the distance of the first shear reinforcement perimeter in relation to the column face (s_0) and the spacing between subsequent perimeters (s_r). In the case of the first layer (s_0), Eurocode 2 [2] recommends at least a distance of $0,3d$. NBR 6118 [3] recommends that it is at most $0,5d$, where d is the

effective depth of the slab. For the space between subsequent perimeters (s_r), these codes suggest a maximum distance of $0,75d$. Limitations for these values are important (see Figure 5). If the first perimeter of studs is placed too close to the column (very small s_0) their lower anchorage may be poor. The same may happen with the posterior perimeters, but in their upper anchorages, if the space between layers is very high. In both cases, poor anchorage conditions may favor punching failures before the shear reinforcement yields.

3. Theoretical methods for estimation of the punching resistance

The codes considered in this paper and the Critical Shear Crack Theory admit that the punching resistance of flat slabs with shear reinforcement should be taken as the smaller value be-

Figure 5 – Zones with critical anchorage conditions

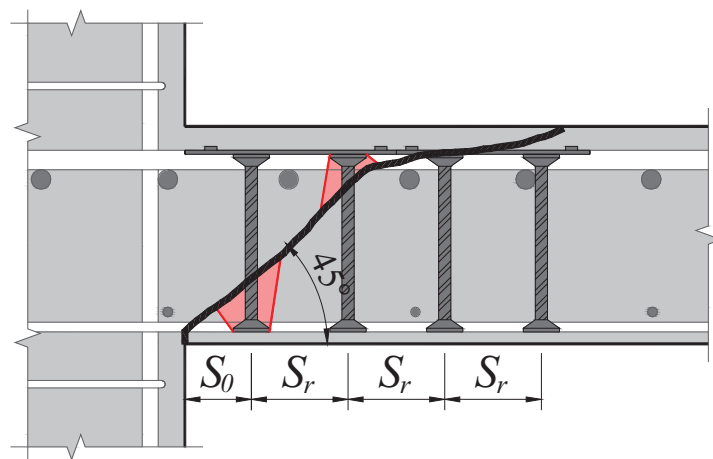

tween $V_{R,cs}$, $V_{R,out}$ and $V_{R,max}$, corresponding to the failure modes indicated in Figure 3, but not lower than $V_{R,c}$, which is the punching resistance of a slab with the same characteristics but without shear reinforcement. In the case of design codes, for the estimation of the punching resistance, the general principle adopted is to assume a constant resistant stress along different control perimeters. These control perimeters are admitted at specific distances from the column face, still having different geometries. The control perimeter u_0 is used to estimate the maximum punching resistance of a slab-column connection ($V_{R,max}$). The control perimeter u_1 is associated to the resistance to diagonal tension in the proximities of the column face, being used for the calculation of $V_{R,c}$ and $V_{R,cs}$. Finally, u_{out} is a perimeter associated to the resistance to diagonal tension in the external area of the shear reinforcement, being associated to $V_{R,out}$. The Critical Shear Crack Theory brings a methodology for the estimation of the punching resistance different from the one presented by the design codes.

3.1 ACI 318M

The ACI expressions for the estimation of the punching resistance are presented in the Equations from 1 to 5. Figure 6 presents some recommendation for the arrangement of the reinforcements and for the definition of the control perimeters. ACI presents specific expressions for the estimation of the punching resistance of flat slabs reinforced with studs. These equations are more optimistic in terms of considering the contribution of studs in the final punching resistance of slab-column connections ($V_{R,s}$), if compared to the equations presented for all other kinds of shear reinforcement, showing that ACI assumes that studs

present anchorage performance significantly higher than all other available shear reinforcements.

$$V_{R,c} = \frac{1}{3} \cdot \sqrt{f_c} \cdot u_1 \cdot d \tag{1}$$

$$V_{R,cs} = 0,75 \cdot V_{R,c} + V_{R,s} \tag{2}$$

$$V_{R,s} = \frac{d}{s_r} \cdot A_{sw} \cdot f_{yw}, \text{ with } f_{yw} \leq 414 \text{ MPa} \tag{3}$$

$$V_{R,out} = \frac{1}{6} \cdot \sqrt{f_c} \cdot u_{out} \cdot d \tag{4}$$

$$V_{R,max} = \frac{2}{3} \cdot \sqrt{f_c} \cdot u_1 \cdot d, \text{ if } s_r \leq 0.5d \tag{5a}$$


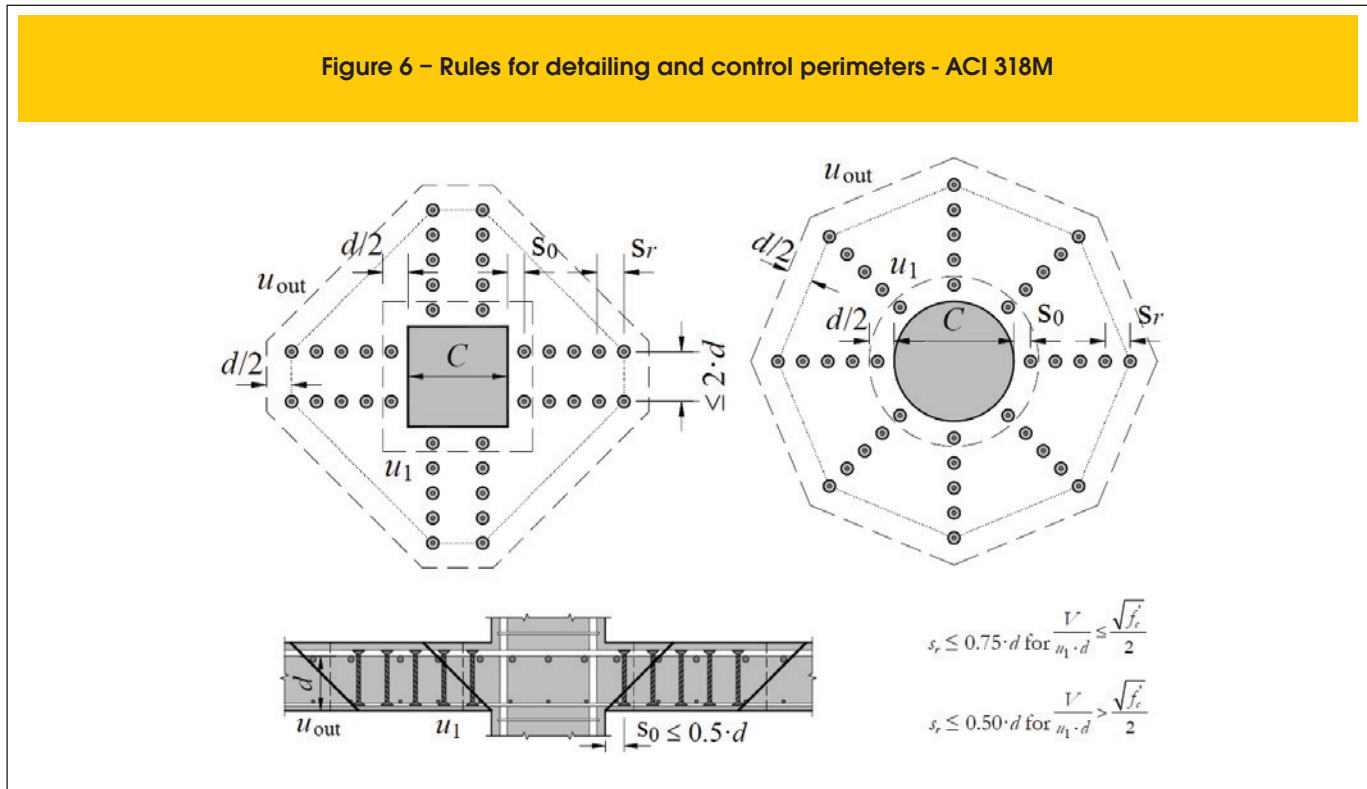


Figure 7 – Rules for detailing and control perimeters – NBR 6118

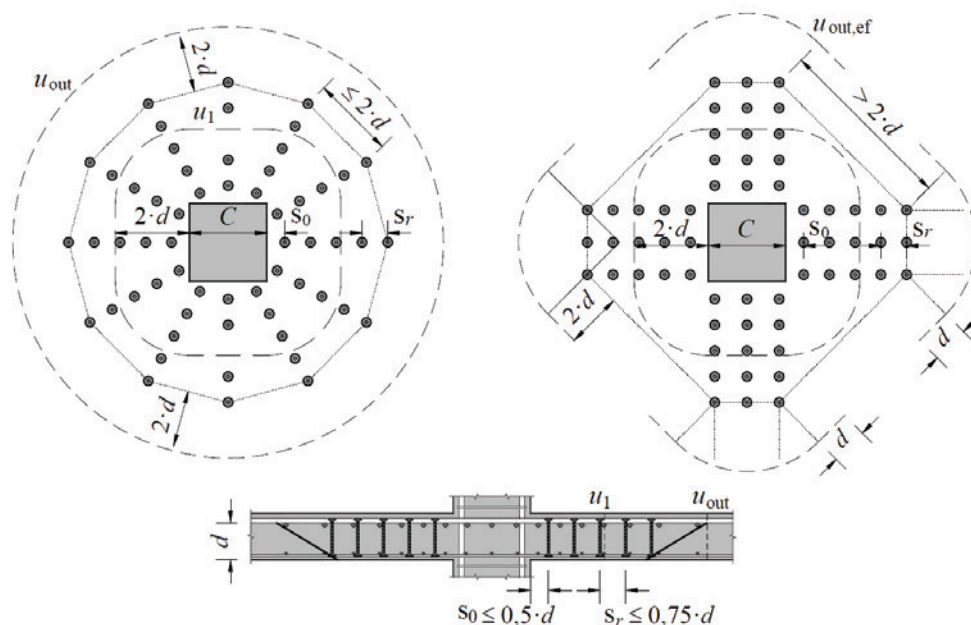

$$V_{R,max} = \frac{1}{2} \cdot \sqrt{f_c} \cdot u_1 \cdot d, \text{ if } 0,5d \leq s_r \leq 0,75d \quad (5b)$$

f_c is limited to ≤ 69 MPa for calculation purposes.
 A_{sw} is the area of steel of a layer of shear reinforcement;
 f_{yw} is the yield stress of the shear reinforcement, not higher than 420 MPa.

3.2 NBR 6118

The Brazilian code used as reference the design process adopted in CEB-FIPMC90 [13], presenting practically the same equations of this code, with small modifications, like the geometry of the external control perimeter for the case of slabs with reinforcements distributed in a radial form, which, in the case of the Brazilian code is circular. These recommendations are presented in a synthesized manner in the Equations 6 to 9 and in Figure 7. Notice that in this paper the equations are presented without the safety coefficient of 1.4, which is implicit in the expressions presented by the Brazilian code.

$$V_{R,c} = 0,18 \cdot \xi \cdot (100 \cdot \rho \cdot f_c)^{1/3} \cdot u_1 \cdot d \quad (6)$$

$$V_{R,cs} = 0,75 \cdot V_{R,c} + \left(1,5 \cdot \frac{d}{s_r} \cdot A_{sw} \cdot f_{yw,ef} \right) \quad (7)$$


$$V_{R,out} = 0,18 \cdot \xi \cdot (100 \cdot \rho \cdot f_c)^{1/3} \cdot u_{out} \cdot d \quad (8)$$

$$V_{R,max} = 0,27 \cdot \alpha_v \cdot f_c \cdot u_0 \cdot d \quad (9)$$

where
 f_c is limited to 50 MPa for calculation purposes;
 ρ is the average tensioned flexural reinforcement ratio of the slab, calculated as $\rho = \sqrt{\rho_x \cdot \rho_y}$,
 where ρ_x and ρ_y are the ratios in the directions x and y, respectively;
 A_{sw} is the steel area of perimeters of shear reinforcement;
 ξ is the size effect, assumed as $\xi = 1 + \sqrt{\frac{200}{d}}$, with d in mm;

$$\alpha_v = \left(1 - \frac{f_c}{250} \right) \text{ with } f_c \text{ in MPa}$$

Figure 8 – Rules for detailing and control perimeters – Eurocode 2

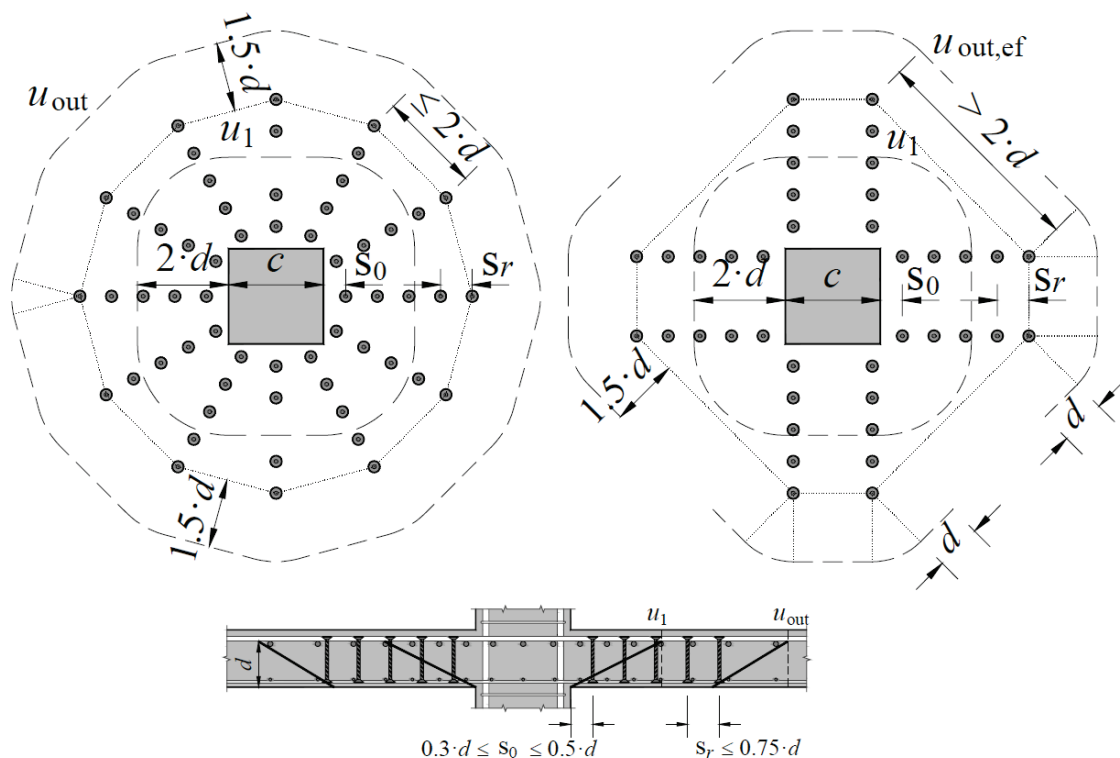

f_{yw} is the yield stress of the shear reinforcement, not higher than 345 MPa for studs or 288 MPa for stirrups (steel CA-50 or CA-60).

3.3 Eurocode 2

Eurocode 2 [2] was also based on MC90. It presents recommendations similar to the ones available in the Brazilian code. The main differences between the prescriptions set by this code are the limitation of the size effect value in $k \leq 2,0$, the limitation of the flexural reinforcement ratio that effectively contributes in the punching resistance, considered as $\rho \leq 2\%$ and the determination of the effective stress in the shear reinforcement. The equations 10 to 16 summarize the expressions presented by this code and Figure 8 helps in the determination of the control perimeters and in the reinforcement spacing.

$$V_{R,c} = 0,18 \cdot k \cdot (100 \cdot \rho \cdot f_c')^{1/3} \cdot u_1 \cdot d \quad (10)$$

$$k = 1 + \sqrt{200/d} \leq 2,0 \quad (11)$$

$$V_{R,cs} = 0,75 \cdot V_{R,c} + V_{R,s} \quad (12)$$

$$V_{R,s} = 1,5 \cdot \frac{d}{s_r} \cdot A_{sw} \cdot f_{yw,ef} \quad (13)$$

$$f_{yw,ef} = 1,15 \cdot (250 + 0,25 \cdot d) \leq f_{yw,ef} \leq 600 \text{ MPa} \quad (14)$$

$$V_{R,out} = 0,18 \cdot k \cdot (100 \cdot \rho \cdot f_c')^{1/3} \cdot u_{out,ef} \cdot d \quad (15)$$

$$V_{R,max} = 0,30 \cdot f_c \cdot \left(1 - \frac{f_c}{250}\right) \cdot u_0 \cdot d \quad (16)$$

Where:

ρ is the flexural reinforcement ratio calculated as $\rho = \sqrt{\rho_x \cdot \rho_y}$, where ρ_x and ρ_y are the reinforcements ratios in orthogonal directions determined for strips with width equals to the side of the column plus $3 \cdot d$ for both sides;

$\rho \leq 0,02$ for calculating purposes;

$f_c \leq 90$ MPa.

3.4 Critical shear crack theory (CSCT)

This theory is based on the idea that the punching resistance decreases with the increase of the slab rotation, which can be explained by the arising of a critical shear crack that propagates through the slab cutting the compressed diagonal that transmits the shear force to the column (see Figure 9a). The opening of this crack reduces the resistance of the compressed strut and may eventually lead to a rupture by punching. According to Muttoni and Schwartz [14] the width of this crack is proportional to the product $\psi \cdot d$ (see Figure 9b). The shear transmission in the critical crack is directly connected to the roughness of its superficies which is a function of the maximum size of the coarse aggregate. Based on these concepts, Muttoni [15] proposes that the shear resistance piece given by the concrete may be estimated according to the Equation 17. Figure 10 presents the position and the geometry of the control perimeters according to CSCT.

$$V_{R,c} = \frac{3}{4} \cdot \frac{u_1 \cdot d \cdot \sqrt{f_c}}{1 + 15 \cdot \frac{\psi \cdot d}{d_{g0} + d_g}} \quad (17)$$

Where:

ψ is the slab rotation;

d_{g0} is the reference diameter of the aggregate admitted as 16 mm;

d_g is the maximum aggregate diameter used in the slab concrete. The resistance piece provided by the vertical shear reinforcements cut by the rupture superficies can be obtained through Equation 18.

$$V_{R,s} = \sum A_{sw} \cdot f_{sw} \quad (18)$$

Where:

Σ is made for the shear reinforcements cut by the rupture superficies;

A_{sw} is the steel area of a layer of the shear reinforcement;

f_{sw} is the stress on each reinforcement layer, one in function of the details of the shear reinforcement and of the vertical displacements δ_v (see Equation 19) in each reinforcement layer at the point intercepted by the rupture superficies (see Table 1).

$$\delta_v = \frac{\psi \cdot s}{2 \cdot \sqrt{2}} \quad (19)$$

Figure 9 – Propagation of Critical Shear Crack - Adapted from Ruiz and Muttoni (4)


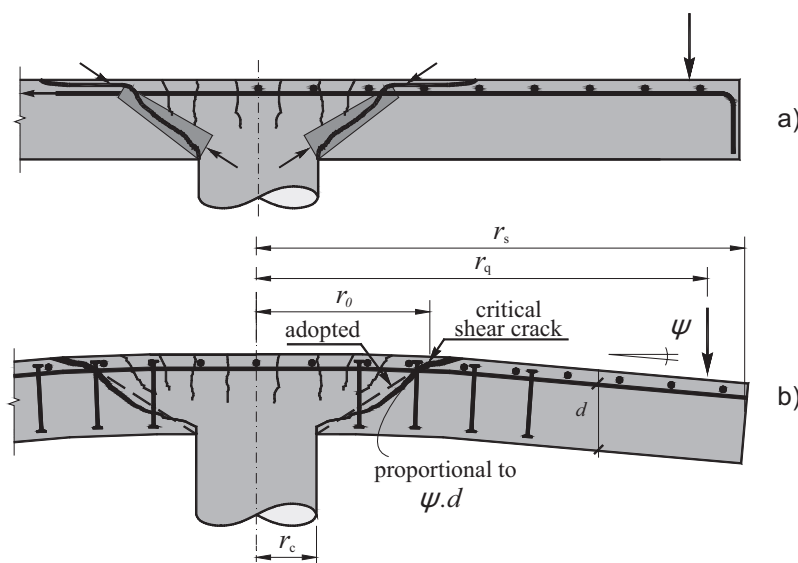


Figure 10 – Rules for detailing and control perimeters – CSCT

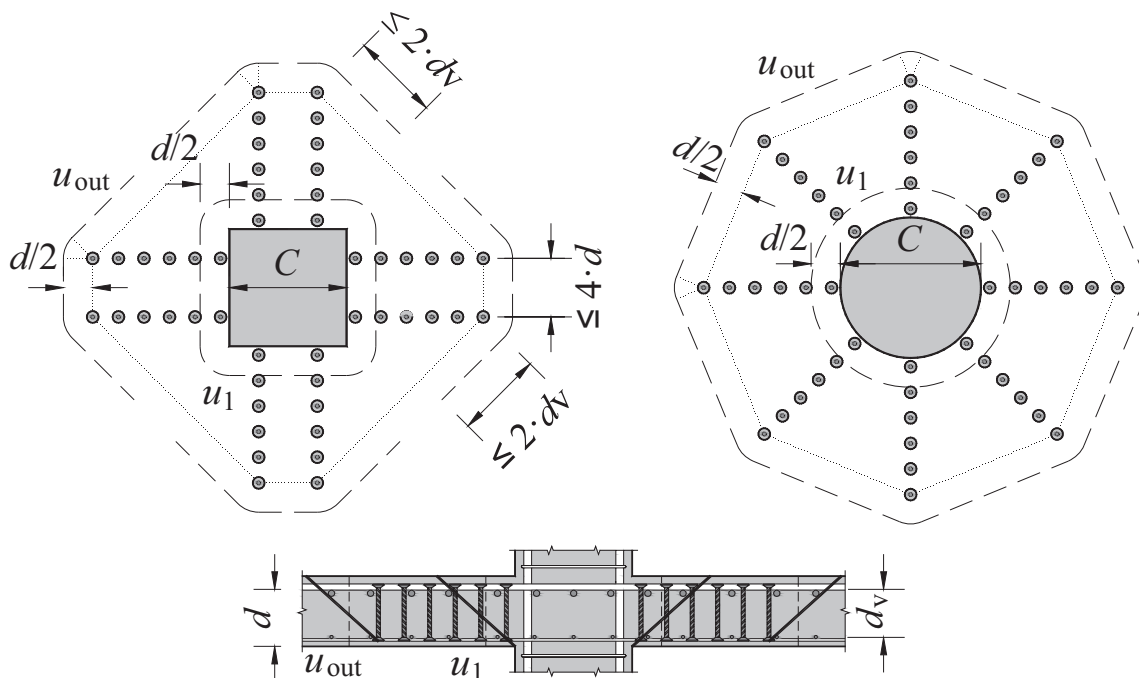

Where:

s is the horizontal distance measured from the face of the column up to the layer of the shear reinforcements concerned.

The punching resistance of a flat slab of reinforced concrete with vertical shear reinforcement can be obtained through Equation 20, being this function of ψ . The relation between the applied charge (V_E) and ψ rotation is expressed by Equation 21.

$$V_{R,\sigma} = V_{R,c} + V_{R,s} \tag{20}$$

$$\psi = 1,5 \cdot \frac{r_s}{d} \cdot \frac{f_{ys,f}}{E_{s,f}} \cdot \left(\frac{V_E}{V_{flex}} \right)^{3/2} \tag{21}$$

Where:

r_s is the distance between the column axis and the null moment's line;

$f_{ys,f}$ is the yield stress of the flexural reinforcements;

$E_{s,f}$ is the elasticity module of the flexural reinforcements;

V_E is the applied force;

V_{flex} is the resistance to flexion calculated through the theory of the rupture lines.

The resistance $V_{R,max}$ corresponding to the rupture by crushing

of the compressed diagonal close to the column and can be calculated by Equation 22.

$$V_{R,max} = \lambda \cdot V_{R,c} \tag{22}$$

Where:


λ is considered equals 3 for the cases of shear reinforcements well anchored like studs and 2 for the other types of shear reinforcements. In the case of ruptures occurring out of the region of the shear reinforcements we admit that the rupture superficies will also have inclination of 45°, but its extremity coincides with the inferior anchorage point of the most external shear reinforcement. In practice, this implies in the reduction of the effective depth of the slab (d) to an effective depth (d_v), as can be seen in Figure 11. The control perimeter in this case is taken at a $d/2$ distance from the perimeter of the most external shear reinforcement layer. Equation 23 must be used for the calculation of V_{Rout} .

$$V_{R,out} = \frac{3}{4} \cdot \frac{u_{out} \cdot d_v \cdot \sqrt{f'_c}}{1 + 15 \cdot \frac{\psi \cdot d}{d_{g0} + d_g}} \tag{23}$$

Where:

u_{out} is the external perimeter defined at a $d/2$ distance from the

Table 1 - Relationship between f_{sw} and δ_v in studs with deformed bars

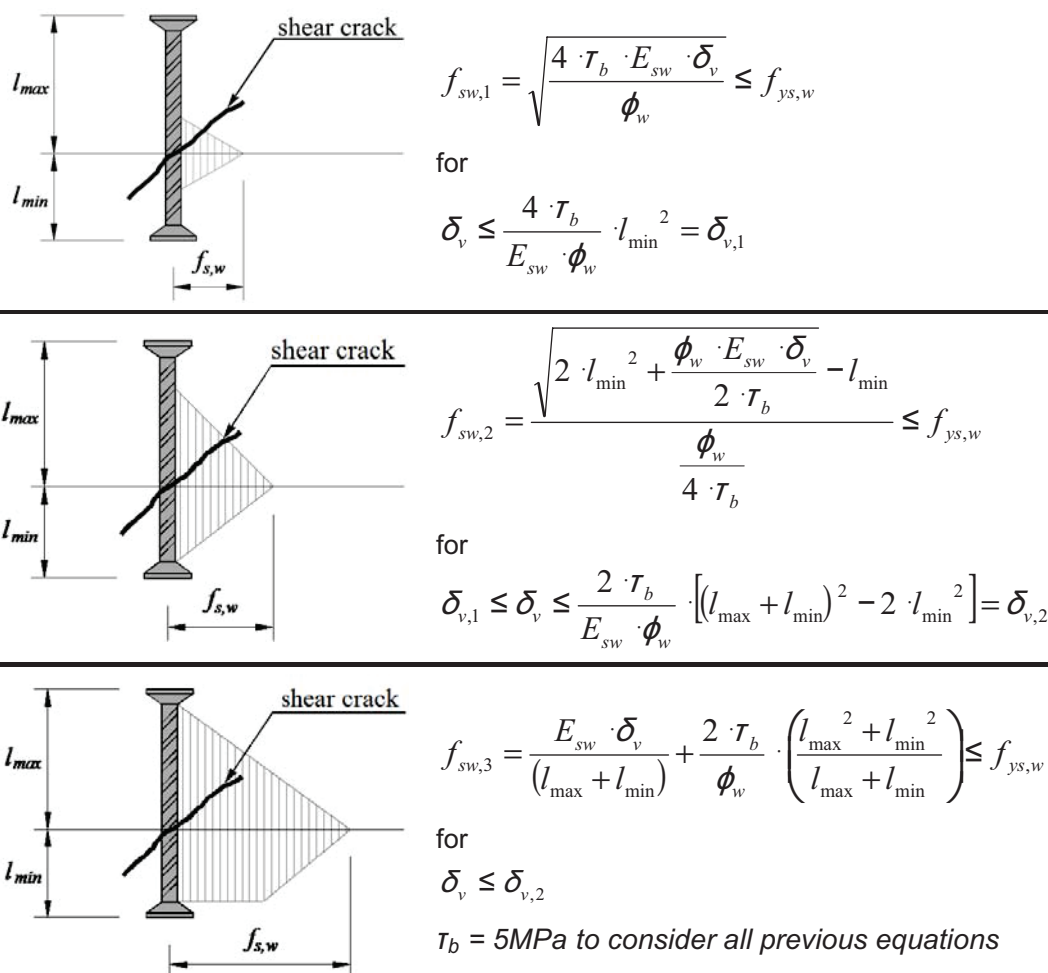

most external layer of the reinforcements, considering $4 \cdot d$ as the maximum effective distance between two concentric lines of shear reinforcements;
 d_v is the reduced effective depth.

The Critical Shear Crack Theory is a graphic method for the determination of the punching resistance. The calculation process begins with the construction of a curve that relates the shear forces with the rotation of the slab-column connection, using the terms V_E

Figure 11 - Failure in the region outside the shear reinforcement - Ruiz and Muttoni (4)


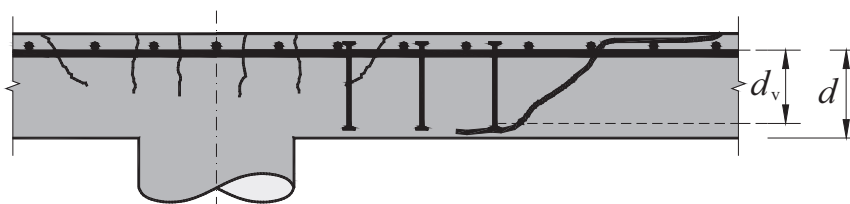


Figure 12 – Example of the estimation of punching shear strength according to the CSCT

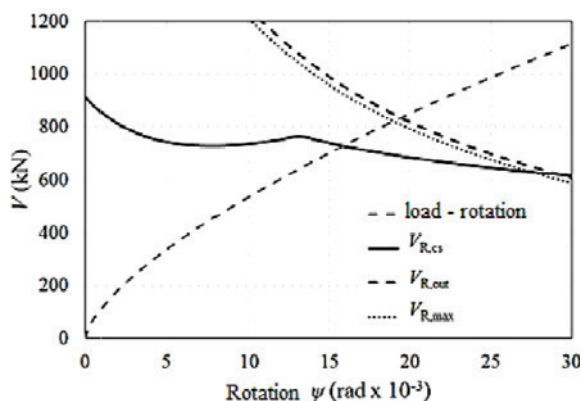

and ψ . Subsequently, this graphic is added to the rupture criteria set by the equations presented above, generating curves $V_{R,cs} - \psi$, $V_{R,Max} - \psi$ e $V_{R,out} - \psi$. The intersection point of these resistance curves with the load-rotation curve defines the connection resistance for each one of the rupture modes. Figure 12 illustrates the graphic process used for the estimation of the resistance to punching according to CSCT.

4. Analysis of theoretical methods

The results presented and evaluated in this paper are originated from the creation of a data basis that counts on results obtained by several authors who studied the case of the flat slabs with shear reinforcement and submit to symmetric loading. It was sought in the formation of this data basis to select only results of reinforced slabs with double-headed studs or with other types of reinforcement which present similar mechanical behavior, once these reinforcements are intentionally considered the most efficient in the resistance to punching due to its best mechanical anchorage. Thus, the data basis counts only on the results of 36 experimental tests. It was opted not to use results of slabs with other kinds of shear reinforcement, to evaluate the accuracy and appropriation of the hypothesis admit by the theoretical methods previously presented to estimate the punching resistance in cases of slabs with shear reinforcement considered of a good anchorage. Slabs tested by Regan [16], Birkle [17], Regan and Samadian [10], Gomes and Regan [18] and Cordovil [19] were selected.

Regan [16] slabs were not published in scientific media of public access, so these results were passed through personal correspondence with the author, having its proper authorial concession. From the slabs tested by Birkle [17], nine slabs had shear reinforcement and three slabs were used as reference. This author's slabs are important due to the elevated thickness they had, providing valuable results in relation to the size effect. All of the selected slabs tested by Regan and Samadian [10] presented shear reinforcements type double-headed stud, being their results important for the evaluation of the prescriptions for rupture modes occurring out of the area with shear reinforcement. From the 11 slabs

Table 2 - Criteria for evaluating V_u/V_{teo}

Criteria for evaluating	Classification
$V_u/V_{teo} < 0,95$	Unsafe
$0,95 \leq V_u/V_{teo} \leq 1,15$	Precise
$1,15 < V_u/V_{teo} \leq 1,30$	Satisfactory
$V_u/V_{teo} > 1,30$	Conservative


tested by Gomes and Regan [18], one of them did not have shear reinforcement and ten had reinforcements formed by slices of I sections, having these reinforcements mechanical behavior similar to double-headed studs. Finally, from the slabs tested by Cordovil [19], three slabs had shear reinforcement and one slab was used as reference. These slabs provided results for small thicknesses and for the use of shear reinforcement ratio relatively low.

The analyses performed in this article consisted basically of comparing the rupture load obtained in the tests with the theoretical loads estimated by the methods presented. To evaluate the accuracy and the safety of these theoretical methods, these authors set the criterion presented on Table 2, which has as a basis the relation V_u/V_{teo} (being V_u the last test charge and V_{teo} the last load estimated by the theoretical method under evaluation). Figure 13 presents general characteristics of the slabs used in the data basis and Table 3 shows all the variables of the tested models, used as entry values in the calculations performed. Table 4 presents the results of the tests and the theoretical estimations, besides a simplified statistic evaluation, considering the results average and its respective coefficient of variations.


Analyzing the results of the North American code ACI 318M [1], it becomes evident that among all estimations of ultimate load, this one presented the most conservative predictions, having for the relation V_u/V_{ACI} a 1.48 average value and a 0.19 coefficient of variation. This fact is associated to the fact that this code underestimates the contribution of the steel for the punching resistance. Comparing these expressions to consider the contribution of the ACI concrete to the ones of Eurocode and with the ones of NBR 6118, we have $V_{R,cACI}/V_{R,cEC2}$ has a 0.85 average value and for NBR the relation $V_{R,cACI}/V_{R,cNBR}$ has a 0.79 average value. It proves the conservatism of ACI in relation to the piece of contribution of the concrete in the punching resistance. This same conservatism is seen when compared to the relation of the steel resistance parcel $V_{R,sACI}/V_{R,sEC}$ with a 0,86 average value and the relation $V_{R,sACI}/V_{R,sNBR}$ with a 0.76 average value.

This code also presents a strong tendency to predict ruptures in a critical perimeter out of the area of the shear reinforcement, presenting this kind of rupture in 89% of its predicts, besides presenting in a general way a mistake of 45% in all predictions of the rupture superficies. Although ACI considers at a more appropriate form for the anchorage condition of the different types of shear reinforcement, its conservatism in relation to the resistant capacity of the materials perhaps must be reevaluated. This fact leads to the discussion that the North American code might have its prescriptions adjusted for the case analyzed here, aiming at avoiding


Figure 13 – Details of the slabs of the database

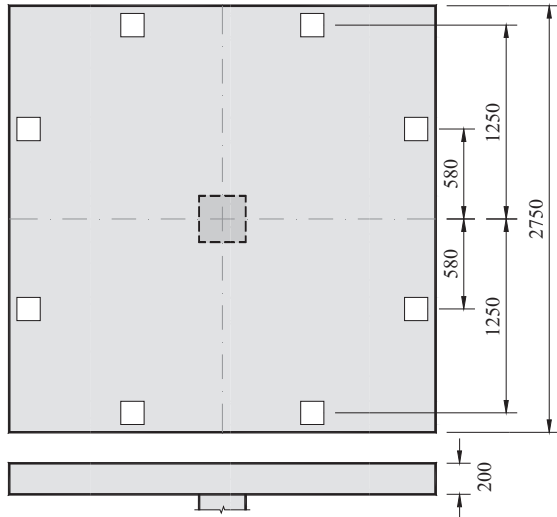


A Regan (16)

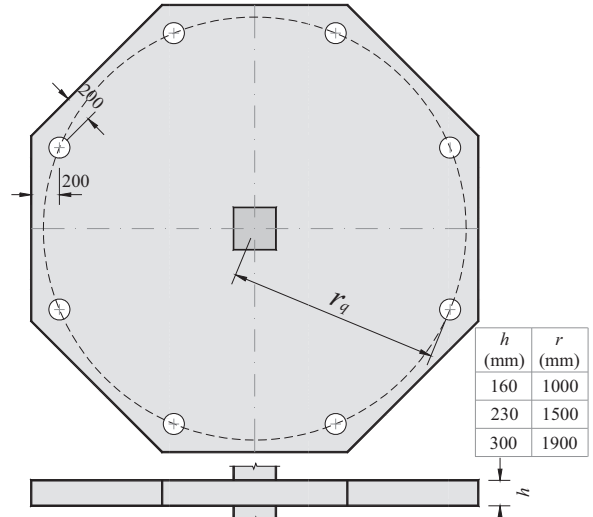

B Birkle (17)

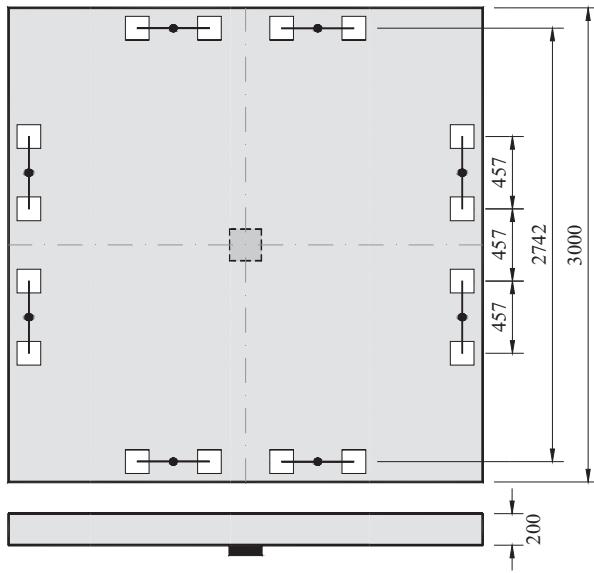

C Gomes e Regan (18); Regan and Samadian (10)

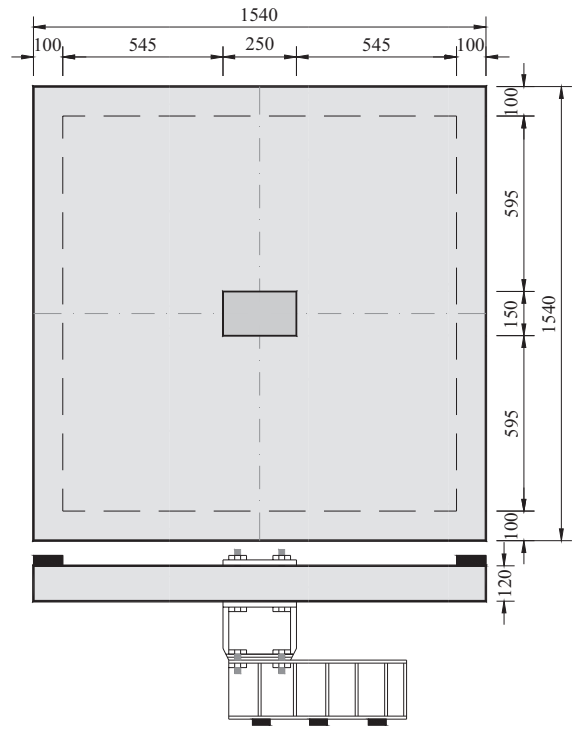

D Cordovil (19)

- : cylinder or tie causing two loads or reactions;
- : cylinder or tie; (cylinders below the columns not shown)

safety levels considered exaggerated and which may lead to an anti-economics dimensioning.

Evaluating NBR 6118 [3] and having as a basis the classification of the normative performance level presented in Table 4, it is possible to say that this code presents very accurate average results. Although it has presented relation V_U/V_{NBR} with a 0.97 general average and a 0.11 coefficient of variation, the safety level of the equations of NBR 6118 is questionable, once that for 64% of the slabs its results were against safety, with the code estimating a

resistant capacity superior to the one observed in the tests. In relation to the prediction of the rupture superficies, this code presented results considered satisfactory, hitting 71% of its Predictions.

Among the analyzed codes, Eurocode 2 [2] was the one that presented the best results, presenting for the relation V_U/V_{EC2} a 1.13 average value, a 0.12 coefficient of variation and only 11% of results against safety. However, the results presented in Table 3 show that EC2 presents a strong tendency to predict rupture out of the area with shear reinforcement, having predicted this kind of

Table 3 – Slabs characteristics

Author	Slab	d (mm)	c (mm)	ρ (%)	ϕ_w (mm)	Lines	$A_{sw}/$ Layer (mm ²)	Perimeters	s_n (mm)	s_s (mm)	f_c (MPa)	f_{ys} (MPa)	E_{cf} (GPa)	$f_{ys,w}$ (MPa)	$E_{s,w}$ (GPa)	d_g (mm)
Regan (2009)	1	150	300	1,45	10	10	785	4	80	120	33	550	210	550	210	20,0
	2	150	300	1,76	10	12	942	6	60	100	30	550	210	550	210	20,0
	3	150	300	1,76	12	10	1.131	5	60	120	26	550	210	550	210	20,0
Birkle (2004)	S1	124	250	1,53	-	-	-	-	-	-	36	488	195	-	-	14,0
	S2	124	250	1,53	10	8	567	6	45	90	29	488	195	393	200	14,0
	S3	124	250	1,53	10	8	567	6	45	90	32	488	195	393	200	14,0
	S4	124	250	1,53	10	8	567	5	30	60	38	488	195	465	200	14,0
	S5	124	250	1,53	10	8	567	7	30	60	36	488	195	465	200	14,0
	S6	124	250	1,53	10	8	567	7	30	60	33	488	195	465	200	14,0
	S7	190	300	1,29	-	-	-	-	-	-	35	531	200	-	-	20,0
	S8	190	300	1,29	10	8	567	5	50	100	35	531	200	460	200	20,0
	S9	190	300	1,29	10	8	567	6	75	150	35	531	200	460	200	20,0
	S10	260	350	1,10	-	-	-	-	-	-	31	524	200	-	-	20,0
	S11	260	350	1,10	13	8	1.013	5	65	130	30	524	200	409	200	20,0
	S12	260	350	1,10	13	8	1.013	6	95	195	34	524	200	409	200	20,0
Regan and Samadian (2001)	R3	160	200	1,26	12	8	905	4	80	120	33	670	210	442	210	20,0
	R4	160	200	1,26	12	8	905	6	80	80	39	670	210	442	210	20,0
	A1	160	200	1,64	10	8	628	6	80	80	37	570	210	519	210	20,0
	A2	160	200	1,64	10	8	628	4	80	120	43	570	210	519	210	20,0
	R5	240	500	0,72	14	12	1.847	4	90	60	32	550	210	350	210	20,0
	R6	236	350	0,67	14	8	1.232	5	70	140	25	550	210	350	210	20,0
Gomes and Regan (1999)	1	159	200	1,27	-	-	-	-	-	-	40	680	215	-	-	20,0
	2	153	200	1,32	6	8	226	2	80	80	34	680	215	430	205	20,0
	3	158	200	1,27	7	8	301	2	80	80	39	670	185	430	205	20,0
	4	159	200	1,27	8	8	402	3	80	80	32	670	185	430	205	20,0
	5	159	200	1,27	10	8	628	4	80	80	35	670	185	430	205	20,0
	6	159	200	1,27	10	8	628	4	80	80	37	670	185	430	205	20,0
	7	159	200	1,27	12	8	905	5	80	80	34	670	185	430	205	20,0
	8	159	200	1,27	12	8	905	6	80	80	34	670	185	430	205	20,0
	9	159	200	1,27	12	8	940	9	80	80	40	670	185	430	205	20,0
	10	154	200	1,31	6	8	226	5	80	80	35	670	185	430	205	20,0
	11	154	200	1,31	7	8	301	5	80	80	35	670	185	430	205	20,0
Cordovil (1995)	7	131	100	0,85	-	-	-	-	-	-	34	500	199	-	-	19,0
	8	131	100	0,85	6,3	8	249	3	70	100	34	500	199	320	199	19,0
	11	131	100	0,85	6,3	8	249	3	70	100	34	500	199	320	199	19,0
	14	104	250/1	0,88	6,3	8	249	3	53	90	30	500	199	320	199	19,0

rupture in 74% of the slabs with shear reinforcement which are in the data basis. This same behavior was also noticed by Ferreira [17] and is associated to the conservatism of the prescriptions for

the definition of the external control perimeters (u_{out} e $u_{out,eff}$). In his work, Ferreira [17] analyzed the possibility of changing the distance of detachment of u_{out} in relation to the last reinforce-

Table 4 – Relationship between the experimental results and theoretical methods

Author	Slab	V_u (kN)	Failure surface	NBR -2007		EC2 -2004		ACI -2008		TFCC	
				V/V_{NBR}	Failure surface NBR	V/V_{EC2}	Failure Surface EC2	V/V_{ACI}	Failure Surface ACI	V/V_{TFCC}	Failure Surface TFCC
Regan (2009)	1	881	in	0,85	out	1,02	out	1,45	out	0,98	out
	2	1.141	fc/out	0,94	out	1,13	out	1,71	out	1,17	out
	3	1.038	fc/in	1,00	out	1,22	out	1,73	out	1,09	out
Birkle (2004)	S1	435	Ref.	0,97	Ref.	1,11	Ref.	1,30	Ref.	1,13	Ref.
	S2	480	in	0,92	out	1,19	out	1,24	out	1,06	in
	S3	513	in	0,91	out	1,12	out	1,10	out	1,04	in
	S4	526	out	0,93	out	1,21	out	1,67	out	1,11	out
	S5	518	out	0,93	out	1,21	out	1,67	out	1,10	out
	S6	522	out	0,96	out	1,18	out	1,67	out	1,08	out
	S7	874	Ref.	0,92	Ref.	0,94	Ref.	1,12	Ref.	1,00	Ref.
	S8	1.070	in	0,84	out	0,98	out	1,29	out	0,91	in
	S9	1.025	in	0,98	in	1,06	in	1,28	in	1,10	in
	S10	1.335	Ref.	0,77	Ref.	0,78	Ref.	0,88	Ref.	0,84	Ref.
	S11	1.626	in	0,86	out	1,00	out	1,24	out	0,93	in
	S12	1.687	in	0,82	in	0,90	out	1,03	in	1,00	in
Regan and Samadian (2001)	R3	850	out	0,85	out	1,04	out	1,44	out	1,05	in
	R4	950	out	0,90	out	1,10	out	1,39	out	1,12	in
	A1	1.000	out	0,88	out	1,08	out	1,50	out	1,20	in
	A2	950	in	0,93	in	1,03	in	1,42	out	1,10	in
	R5	1.440	out	0,95	out	1,09	out	1,08	out	1,07	out
	R6	1.280	flex	0,91	out	1,02	out	1,05	out	0,88	in
Gomes and Regan (1999)	1	560	Ref.	0,88	Ref.	0,94	Ref.	1,16	Ref.	1,02	Ref.
	2	693	in	1,14	in	1,26	in	1,64	out	1,19	in
	3	773	in/out	1,10	in	1,21	in	1,64	out	1,22	in
	4	853	out	1,03	out	1,27	out	1,98	out	1,36	in
	5	853	out	1,01	out	1,24	out	1,77	out	1,21	in
	6	1.040	out	1,01	out	1,23	out	2,07	out	1,44	in
	7	1.120	out	1,13	out	1,38	out	2,02	out	1,43	in
	8	1.200	out	1,20	out	1,48	out	1,90	out	1,53	in
	9	1.227	out	0,92	out	1,09	out	1,70	Max	1,49	in
	10	800	in	1,16	in	1,28	in	1,58	in	1,39	in
	11	907	in	1,18	in	1,31	in	1,68	out	1,52	in
Codovil (1995)	7	320	Ref.	0,96	Ref.	1,08	Ref.	1,36	Ref.	1,05	Ref.
	8	400	in	0,98	in	1,05	in	1,42	in	1,11	in
	11	412	in	1,01	in	1,09	in	1,47	in	1,16	in
	14	302	in	0,86	in	1,07	out	1,30	out	0,97	in
Average				0,97		1,13		1,48		1,16	
C.V				0,11		0,12		0,19		0,15	

Ref - reference slab (without shear reinforcement); in - failure surface position within the region of shear reinforcement; out - failure surface position outside the region of shear reinforcement; Max - failure by crushing the concrete strut; flex - flexural strength;

Note: all reference slabs failure by punching.

ments layer of $1.5d$ to $2d$ and altering the criterion of the maximum transversal spacing between layers ($s_{t,max}$) of $2d$ to $4d$. The author observed that such actions would substantially improve the predictions for $V_{R,out}$, being more appropriate to the experimental evidences, but require adjusts also in the equation for $V_{R,CS}$, otherwise, this code would be thought of presenting a substantial number of results against safety. An alternative that may solve this problem would be to reduce the adjust coefficient of the Equation 10 from 0.18 to 0.16 as discussed by Sacramento *et al.* [21] and also by Oliveira [22].

The Critical Shear Crack Theory (CSCT) showed satisfactory results, having a 1.16 average value for the relation V_u/V_{TFCC} and a 0.15 coefficient of variation, with performance similar to EC2. In relation to the prediction of the rupture superficies, on the contrary of the other codes, CSCT presented a tendency to predict ruptures inside the area of the shear reinforcements, predicting this kind of rupture in 74% of the slabs of the data basis. Even though its predicts for the slabs rupture mode was inappropriate, being wrong about the position of the rupture superficies in 37% of the evaluated cases.

5. Conclusions

This paper discusses the use of shear reinforcements as one of the best manners to increase the punching resistance and the ductility of slab-column connections. It also presents in a succinct way the recommendations of the codes ACI 318, NBR 6118 and Eurocode 2, besides the Critical Shear Crack Theory. It was made a small data basis with experimental results of tests in 36 slabs with double-headed studs or similar shear reinforcements, comparing these results with the theoretical ones obtained using the codes and CSCT.

Even considering that the data basis is limited due to the lack of tests with slabs with this kind of shear reinforcement, it is possible to observe that the recommendations presented by ACI may be conservative for the cases of slabs with shear reinforcements with good anchorage. The average of V_u/V_{ACI} was 1.48 and the coefficient of variation was 0.19, substantially superior to the ones observed in the other theoretical methods. This elevated coefficient of variation was already expected once that ACI ignores important parameters in its equations, as the contribution of the flexion reinforcements, besides the reduction of the resistant tension with the increase of the useful height (size effect).

NBR 6118 showed that, despite presenting a 0.97 average results of V_u/V_{NBR} and a 0.11 coefficient of variation, the lowest among the evaluated methods, its equations present a strong tendency of results against safety. At the same moment the low coefficient of variation indicates that the parameters used in its equations present a good correlation with the tendency of the experimental results, the necessity of some adjustments becomes evident to avoid this tendency of insecure results, as it has already been highlighted by Ferreira [20] and Sacramento *et al.* [21].

Eurocode 2, by limiting k and r values, reduced the tendency of insecure results observed for NBR 6118, presenting the best results among the theoretical methods evaluated. For the small data basis presented, Eurocode 2 presented a 1.13 average of the relation V_u/V_{EC2} and a 0.12 coefficient of variation. Even though, it is evident that the authors could not experimentally observe justifications for the limitations imposed by Eurocode 2 for the size

effect and for the flexural reinforcement ratio, considering technically more appropriate to perform adjusts in the coefficients of the formulations.

Brief comments on the Critical Shear Crack Theory must be made. This method showed sensible to the several variables common in the dimensioning of the flat slabs and presented results near the ones of EC2, although slightly more conservative for the data basis in question. In spite of its equations presenting, apparently, a strong empiric basis, the method is very well grounded and explains at a satisfactory mode the punching phenomenon. However, it must be emphasized that, as the method considers that the part of the slab external to the critical shear crack presents only rotations of rigid body and that the sliding of the superficies in the area of this crack does not occur, the method presents the tendency of estimating deformations and, consequently, superior stresses the most distant from the column the shear reinforcements are, when in reality the effect experimentally observed is the opposite. In practice, this may lead to inappropriate results for values of s_0 and s_f near the minimum.

6. Acknowledgements

The authors would like to thank CNPq and CAPES for the financial support in all stages of this research.

7. References

- [01] ACI Committee 318, Building Code Requirements for Structural Concrete (ACI 318-08) and Commentary, American Concrete Institute, Farmington Hills, Michigan, 2008.
- [02] Eurocode 2, Design of Concrete Structures—Part 1-1: General Rules and Rules for Buildings, CEN, EN 1992-1-1, Brussels, Belgium, 2004, 225 pp.
- [03] ASSOCIACAO BRASILEIRA DE NORMAS TECNICAS. NBR 6118 – Projeto de Estruturas de Concreto. Rio de Janeiro, 2007.
- [04] RUIZ, M. F.; MUTTONI, A. Applications of Critical Shear Crack Theory to Punching of Reinforced Concrete Slabs with Transverse Reinforcement. *ACI Structural Journal*, July-August 2009. Nº 106-S46.
- [05] fib Bulletins no. 65 e no. 66, Model Code 2010 – Final draft, Volume 1, 350p, Volume 2, 370p, 2012.
- [06] GRAF, O.. Versuche über die Widerstandsfähigkeit von Eisenbetonplatten unter konzentrierter Last nahe einem Auflager. *Deutscher Ausschuss für Eisenbeton*, Heft 73, Berlin, 1933, 16 pp.
- [07] ELSTNER, R. C., e HOGNESTAD, E., Shearing Strength of Reinforced Concrete Slabs. *Journal of the American Concrete Institute*, Proceedings, V. 53, No. 1, Jul. 1956, pp. 29-58.
- [08] ANDERSON, J. L., Punching of Concrete Slabs with Shear Reinforcement. *Royal Institute of Technology, Bulletin*, No. 212, KTH Stockholm, Sweden, 1963, 59p.
- [09] BROMS, C.E., Elimination of Flat Plate Punching Failure Mode, *ACI Structural Journal*, V. 97, No. 1, Jan.-Feb. 2000, pp. 94-101.

- [10] REGAN, P. E., SAMADIAN, F., Shear Reinforcement against Punching in Reinforced Concrete Flat Slabs, *The Structural Engineer*, V. 79, No. 10, May 2001, pp. 24-31.
- [11] OLIVEIRA, D. R., MELO, G. S., REGAN, P. E., Punching Strengths of Flat Plates with Vertical or Inclined Stirrups. *ACI Structural Journal*, V. 97, No. 3, May-June 2000, pp. 485-491.
- [12] DILGER, W.H., and GHALI, A., Shear Reinforcement for Concrete Slabs, *ASCE Journal of Structural Division, Proceedings*, V. 107, No. ST12, Dec. 1981, pp. 2403- 2420.
- [13] Comité Euro-International du Béton. CEB-FIP Model Code 1990. London, Thomas Telford, 1993.
- [14] MUTTONI, A., and SCHWARTZ, J., Behaviour of Beams and Punching in Slabs without Shear Reinforcement, *IABSE Colloquium*, V. 62, Zurich, Switzerland, 1991, pp. 703-708.
- [15] MUTTONI, A., Punching Shear Strength of Reinforced Concrete Slabs without Transverse Reinforcement, *ACI Structural Journal*, V. 105, No. 4, July-Aug. 2008, pp. 440-450.
- [16] REGAN, P. E., Report on tests of reinforced concrete flat slabs with double-headed studs. Correspondência pessoal com o autor. 2009.
- [17] BIRKLE, G., Punching of Flat Slabs: The Influence of Slab Thickness and Stud Layout. PhD Thesis. Department of Civil Engineering, University of Calgary, Calgary, Canada, 2004, 152 pp.
- [18] GOMES, R. B. e REGAN, P. E., Punching Resistance of RC Flat Slabs with Shear Reinforcement. *Journal of Structural Engineering*, 1999, 684-692.
- [19] CORDOVIL, F. A. B. Punção em Placas de Concreto Armado. Tese de Doutorado, Departamento de Engenharia de Estruturas e Fundações, Escola Politécnica da Universidade de São Paulo, 1995, 393p.
- [20] FERREIRA, M. P. (2010). Punção em Lajes Lisas de Concreto Armado com Armaduras de Cisalhamento e Momentos Desbalanceados. Tese de Doutorado em Estruturas e Construção Civil, Publicação E.TD – 007 A/10 Departamento de Engenharia Civil e Ambiental, Universidade de Brasília, Brasília, DF, 275p.
- [21] SACRAMENTO, P.V.P; FERREIRA, M.P; OLIVEIRA, D.R.C; MELO, G.S.S.A, Punching strength of reinforced concrete flat slabs without shear reinforcement. *IBRACON Structures and Materials Journal*. 2012. vol. 5, nº 5.
- [22] OLIVEIRA, M. H. (2013). Punção Em Lajes Lisas Com Armadura de Cisalhamento Submetidas a Carregamento Excêntrico e Apoiadas Sobre Pilares Retangulares. Tese de Doutorado em Estruturas e Construção Civil, Publicação E.TD – 001 A/13 Departamento de Engenharia Civil e Ambiental, Universidade de Brasília, Brasília, DF, 223p.